

## **Bi(III) immobilization inside MIL-101: enhanced photocatalytic performance**

Kovalenko, K. A.; Ruban, N. V.; Adonin, S. A.; Korneev, D. V.; Erenburg, S. B.;  
Trubina, S. V.; Kvashnina, K.; Sokolov, M. N.; Fedin, V. P.;

Originally published:

January 2017

**New Journal of Chemistry 41(2017)6, 2255-2260**

DOI: <https://doi.org/10.1039/C6NJ03482A>

Perma-Link to Publication Repository of HZDR:

<https://www.hzdr.de/publications/Publ-24389>

Release of the secondary publication  
on the basis of the German Copyright Law § 38 Section 4.

## Bi(III) immobilization inside MIL-101: enhanced photocatalytic performance

Konstantin A. Kovalenko,<sup>a,b\*</sup> Natalia V. Ruban,<sup>b</sup> Sergey A. Adonin,<sup>a,b</sup> Denis V. Korneev,<sup>c</sup> Simon B. Erenburg,<sup>a,d</sup> Svetlana V. Trubina,<sup>a</sup> Kristina Kvashnina,<sup>e,f</sup> Maxim N. Sokolov,<sup>a,g</sup> and Vladimir P. Fedin<sup>a,b</sup>

A novel hybrid material Bi(III)@MIL-101 (Bi(III) = Bi-containing oxoclusters, MIL-101 = chromium(III) oxoterephthalate) was obtained by the intrapore hydrolysis of guest bismuth(III) chloride in ammonia solution. The compound was characterized by chemical analysis, powder X-ray diffraction, nitrogen sorption and TEM techniques. According to the obtained data all Bi species are located only inside the matrix. The framework structure keeps intact during all synthetic operations. The chemical nature of Bi(III)-containing clusters inside MIL-101 matrix was suggested based on the EXAFS study. The catalytic activity of Bi(III)@MIL-101 in photodegradation of methyl red (MR) has been tested. An introduction of Bi(III)-species inside MIL-101 significantly increases the photocatalytic performance in comparison with layered BiOCl which was obtained in the same synthetic conditions without MIL-101.

### INTRODUCTION

Over the last years, development of highly efficient photocatalytic materials represents one of the “hot topics” in modern chemistry. Among the possible application areas, treatment of industrial-use water containing organic pollutants is of special interest due to the great environmental importance.<sup>1–7</sup> In the great family of photoactive compounds which are commonly used (such as TiO<sub>2</sub>, ZnO, CdS etc.), bismuth oxohalides BiOX (X = Cl, Br, I) have been attracting much attention due to their high activity and tunability when used in hybrid materials.<sup>8–18</sup>

The main factors affecting the activity of the photocatalyst are morphology, surface area and size of particles. These characteristics determine the goal of further development of synthetic methods and approaches which currently include solvothermal, microwave-assisted, ionic-liquid and many other routes.<sup>19</sup> The ultimate objectives are: 1) to achieve the biggest surface area, 2) to maximize the stability of catalyst morphology and 3) to find the simplest and cheapest method of synthesis. From this point of view, impregnation of

photocatalyst nanoparticles into a stable porous matrix offers a suitable solution meeting at least two of these three targets. Perfect candidates for this role are metal-organic frameworks (MOFs).<sup>20–29</sup> This class of compounds has been successfully used for immobilization of numerous types of catalysts, e.g. polyoxometalates<sup>30–35</sup> and metal nanoparticles,<sup>36–40</sup> resulting in remarkable improvement of catalytic properties (activity, stability and recyclability) and/or changing homogeneous catalysis into heterogeneous. Also it is best known that MOFs possess their own photocatalytic activity.<sup>2,41</sup> Recently composites of BiOBr and two different MOFs: NH<sub>2</sub>-MIL-125(Ti)<sup>42</sup> and UiO-66(Zr)<sup>43</sup> – were prepared and their enhanced photocatalytic ability were demonstrated.

In this work we present an approach to inclusion compounds of “Bi(III)@MOF” family. Mesoporous chromium(III) terephthalate [Cr<sub>3</sub>O(H<sub>2</sub>O)<sub>2</sub>(bdc)<sub>3</sub>X]·nH<sub>2</sub>O (X = F<sup>–</sup> or NO<sub>3</sub><sup>–</sup>; H<sub>2</sub>bdc = 1,4-benzenedicarboxylic acid; n ≈ 25), commonly referred to as MIL-101, is one of the best known MOFs;<sup>44</sup> it was chosen for the experiments because of its outstanding stability in both acidic and weakly basic media. Inclusion of Bi(III) species into stable MOF matrix results in new photocatalytic system with enhanced activity in comparison with pure layered BiOCl. The photocatalytic properties were examined on a classical organic dye degradation process and methyl red was chosen as a test pollutant because it is known as a potential carcinogenic azo dye. Special point was addressed to establishment Bi(III) particles structure inside MOF cavities.

### RESULTS AND DISCUSSION

Introduction of Bi(III)-species was carried out by standard hydrolysis technique of bismuth(III) chloride in ammonia solution. To avoid formation of Bi(III) species outside the cages of metal-organic framework the two-step approach was used. In a typical experiment, MIL-101 was stirred with a hydrochloric acid solution of BiCl<sub>3</sub>. After filtering off and drying

<sup>a</sup> Nikolaev Institute of Inorganic Chemistry SB RAS, 3 Akad. Lavrentiev Av., 630090 Novosibirsk, Russian Federation. E-mail: [k.a.kovalenko@niic.nsc.ru](mailto:k.a.kovalenko@niic.nsc.ru); Fax: +7 (383) 330 9489, Tel.: +7 (383) 330 9490.

<sup>b</sup> Novosibirsk State University, 2 Pirogova Street, 630090 Novosibirsk, Russian Federation.

<sup>c</sup> State Research Centre for Virology and Biotechnology “Vector”, 630559 Koltsovo, Novosibirsk Region, Russian Federation.

<sup>d</sup> Budker Institute of Nuclear Physics SB RAS, 11 Akad. Lavrentiev Av., 630090 Novosibirsk, Russian Federation.

<sup>e</sup> European Synchrotron Radiation Facility, BP 220, 38043, Grenoble Cedex, France, EU.

<sup>f</sup> Helmholtz-Zentrum Dresden-Rossendorf (HZDR), Institute of Resource Ecology – P.O. Box 510119, 01314, Dresden, Germany, EU.

<sup>g</sup> Kazan Federal University, Alexander Butlerov Institute of Chemistry, Lobachevskogo Street 1/29, 420008, Kazan, Russian Federation.

Electronic Supplementary Information (ESI) available: Further experimental data including PXRD, TEM, N<sub>2</sub> sorption, EXAFS spectra and catalytic tests. See DOI: 10.1039/x0xx00000x

at moderate temperature (ca. 50 °C) solid sample was placed into ammonia solution with vigorous stirring to fix Bi(III) species inside MIL-101 cages. Resulted powder of Bi(III)@MIL-101 was filtered off again and dried in air at 60–70 °C.


Elemental analysis of Bi(III)@MIL-101 reveals that the Cr/Bi ratio is 33.4, which corresponds to 0.09 Bi atoms per  $[\text{Cr}_3\text{O}(\text{btc})_3]^+$  formula unit of MIL-101 or about 1 Bi atoms per MIL mesocage in average. Interestingly, this ratio does not noticeably change when altering the time of impregnation.

To increasing the Bi(III) content the impregnation procedure was repeated several times. After the second impregnation the Cr/Bi ratio decreases down to 15.3. The third cycle additionally decreases the ratio down to 5.0, which is corresponds to 0.6 Bi atoms per formula unit or 6.8 per mesocage in average. The fourth and following impregnations do not alter the Bi content. Meanwhile, the chlorine content in the once impregnated sample is about 0.69 per  $[\text{Cr}_3\text{O}(\text{btc})_3]^+$  formula unit, being higher than Bi content. Therefore, it is impossible to assert stoichiometric bismuth oxochloride formation inside MIL-101 cages. On the other hand it is quite close to the number of tetrahedral microcages (0.5 per f.u.). As it was shown in our previous paper,<sup>45</sup> chloride-anions tend to occupy all such microcages even thanks to fluoride-anions substitution. Therefore, chloride anions together with  $\text{F}^-$  and  $\text{NO}_3^-$  compensate the overall charge of Bi(III)@MIL-101 material.

Transmission electron microscopy (TEM) confirms the absence of both discrete particles and any aggregates of BiOCl or other phases on the surface of MIL-101 crystals for the once impregnated sample. Moreover, it does not visualize any bulky particles of Bi(III) species in the crystals of MIL-101. This fact as well as identical chemical analysis in several nanoscale points have allowed us assuming that the distribution of Bi-containing particles in MIL-101 pores is rather uniform. However, twice and triple impregnated samples significantly differ from the once impregnated sample (Fig. 1): there are a lot of bulky particles on the MIL-101 crystal's surface. Therefore, we can conclude that once impregnated sample is true inclusion compound, whereas after second and third impregnation step at our synthetic conditions the mixture of phases forms.


To confirm the crystallinity of whole sample as well as its phase composition the powder X-Ray diffraction technique was used. PXRD patterns display the absence of peaks corresponding to layered BiOCl which can be obtained in the same synthetic conditions without MIL-101 matrix, initial  $\text{BiCl}_3$  as well as any other phases. Instead, only peaks of MIL-101 were detected (Fig. 2). Slight changes in relative peak intensities (especially in low angle range) are usually observed for inclusion compounds based on MOFs in general, and MIL-101 inclusion compounds in particular.<sup>30,46</sup> Thus, MIL-101 structure is rigid and stable enough both for the procedure of Bi inclusion which proceeds in rather acidic solution (4 M HCl) and for hydrolysis of bismuth chloride in ammonia solution (pH  $\approx$  12).

Attempting to understand the structure of Bi(III)-species inside MIL-101, we have used high-energy-resolution X-ray absorption measurements (EXAFS-HERFD). The measured spectra, comparison of experimental and simulated spectra as

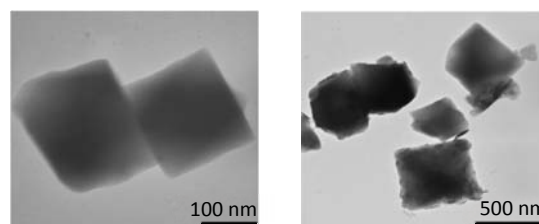


**Fig. 1.** TEM images of Bi(III)@MIL-101 after first (left) and third (right) impregnation.

well as parameters of samples microstructure are given in the ESI (Figs. S3–S5, Table S2). According to these data, the coordination number of bismuth in Bi(III)@MIL-101 is 6 what is different from bismuth coordination number in BiOCl where each Bi binds 4 oxygen and 4 chlorine atoms. Moreover, in spite of quite big chlorine content in Bi(III)@MIL-101 ( $\sim$ 0.7 per formula unit), there are no interactions between Bi and Cl atoms (Table S2). Six coordination sites around each bismuth atom are distributed as follows:  $\sim$ 1 very short bond (2 Å),  $\sim$ 2 short bonds (2.5 Å),  $\sim$ 2 medium bonds (2.7 Å) and 1 long bond (2.9 Å). Analysis of interatomic distances performed for the crystal structures deposited in Cambridge structural database (CSDB) reveals that measured Bi-O distances found in Bi(III)@MIL-101 could correspond to several coordination types summarized in Table S3. Taking into account that there are only two Bi atoms at a distance of 3.24 Å in the vicinity of Bi atoms, in addition to the six oxygen atoms, we could assume predominant formation of trinuclear Bi clusters. The closest Bi-O distance is attributed to  $\mu_3\text{-O}$ , two longer Bi-O distances belong to  $\mu_2\text{-OH}$  or  $\mu_2\text{-OH}_2$ , other two medium bonds may correspond to terminal OH-ligand and the longest Bi-O distance to terminal aqua-ligands, respectively. The proposed structure of bismuth-oxo species is shown in Fig. 3. It must be noted that, according to the CSDB, there are more than 30 compounds containing of such a type of substructural unit (the search was carried out without specifying number of hydrogens) but the most of them are polynuclear clusters. To

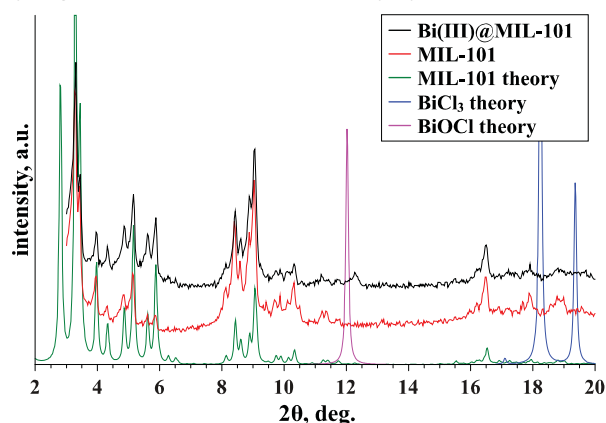

**Fig. 2.** XRPD patterns for Bi(III)@MIL-101 (black) and Cr-MIL-101 (red). Theoretical patterns for MIL-101 (green),  $\text{BiCl}_3$  (blue) and layered BiOCl (pink) are given for comparison.

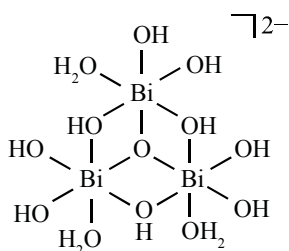

**Fig. 3.** Possible structure of Bi-oxoclusters inside MIL-101.

the best of our knowledge structures of Bi oxocluster strongly depend on synthetic conditions and are very diverse. For example, Loye et al. reported reactions of bismuth nitrate with terephthalic and nitroterephthalic acid in the same synthetic conditions resulted in different structure types containing  $\text{Bi}_2\text{O}_2$ -layer and  $\text{Bi}_4\text{O}_3$ -chain motifs.<sup>47</sup> Oliver et al. have described synthesis, characterisation and some properties of hexa- and nonanuclear cationic clusters and have reported that nature of sulfonic acid, reaction time, temperature and pH are crucial for control the dimensionality of cationic bismuth clusters.<sup>48</sup> Moreover such a type of clusters are known for other metals but their structural characterisation is often very difficult due to their high lability. Thus, Leung et al. have reported crystallisation the hydroxobridged Zr(IV) complexes with Kläui's tripodal ligand.<sup>49</sup> Thuéry have used supramolecular approach by adding cucurbit[6]uril for crystallization of trinuclear clusters with uranyl moieties.<sup>50</sup> It means that unique surrounding of MIL-101 mesocages may result in formation and stabilisation of unusual and still structurally unknown Bi clusters. It means that structure of Bi-containing particles formed in the presence and in the absence of MIL-101 are absolutely different and therefore their catalytic activity should have significant differences too.

Nitrogen sorption isotherms for both Cr-MIL-101 and Bi(III)@MIL-101 have the same shape, which corresponds to mesoporous MOFs (Fig. S6). Principal textural properties for initial MIL-101 and Bi(III)@MIL-101 are summarized in Table 1. Pore volumes obtained for MIL-101 and Bi(III)@MIL-101 are 1.89 and 1.02  $\text{mL}\cdot\text{g}^{-1}$ , respectively. Contemporaneously the BET surface area is decreasing from 3863  $\text{m}^2\cdot\text{g}^{-1}$  for MIL-101 to 2065  $\text{m}^2\cdot\text{g}^{-1}$  for Bi(III)@MIL-101. These facts clearly indicate that Bi particles occupy some space inside the mesocages of MIL-101, although they are still accessible and not blocked by these particles. On the other hand, the micropore volume is significantly decreased for Bi(III)@MIL-101 (see pore size

**Table 1.** Parameters of pore structure for MIL-101 and Bi(III)@MIL-101.


| Compound        | Specific surface area / $\text{m}^2\cdot\text{g}^{-1}$ |      | $V_{\text{pore}} / \text{cm}^3\cdot\text{g}^{-1}$ | $V_{\text{ads}}(\text{N}_2) / \text{cm}^3(\text{STP})\cdot\text{g}^{-1}$ |
|-----------------|--|------|---|--|
|                 | Langmuir   | BET  |   |  |
| MIL-101         | 5762   | 3863 | 1.89  | 1226   |
| Bi(III)@MIL-101 | 2926   | 2065 | 1.02  | 653  |

distribution and cumulative volume curve in Fig. S7 for details); that displays the blocking of microcages of MIL structure after introduction of Bi-containing particles. Taking into account the absence of Bi-Cl interaction found from EXAFS data, significant changes of pore size distribution in MIL-101 and Bi(III)@MIL-101 could be explained by filling of tetrahedral microcages of the framework by chlorine anions whereas Bi(III) containing particles are located in mesocages. The same phenomenon of chlorine distribution into the smaller cavities was established for MIL-101 treated by sodium chloride solution from direct calorimetric experiments which are described in our previous paper.<sup>45</sup>


To investigate the catalytic activity of Bi(III)@MIL-101, photodegradation of methyl red (MR) has been chosen as a test reaction. The full decolorizing of MR solution ( $3.5\cdot 10^{-5}$  M) was observed in 50–60 min under mercury lamp irradiation. The initial rate constant is quite high ( $k = 0.037\pm 0.005 \text{ min}^{-1}$ ,  $\tau_{1/2} = 18 \text{ min } 44 \text{ s}$ ). The process is first-order over the first minutes; consequent changes of kinetics may be related to further oxidation and decomposition of MR primary degradation products (Fig. 4). It should be noted that pure MIL-101 is not active in MR degradation during studied period of time as well as MR is stable under UV-light irradiation during this period (Table S3).

XRPD and element analysis of the sample after the catalytic experiment display that Bi(III)@MIL-101 preserves both composition and crystallinity (Fig. S2 and Table S1). The reaction solution was tested upon leaching of Bi species using atomic absorption spectroscopy. As a result, Bi concentration was found to be below the detection limit of this method (0.5  $\mu\text{g}/\text{mL}$ ) which means that leaching is less than 0.5% (if any). Therefore, we could conclude that the catalytic process has a truly heterogeneous nature.

To check if the activity of Bi(III)@MIL-101 changes in the case when the substrate is added to the solution continually (and the products of MR decomposition are accumulated in solution), "portionwise addition" experiment was conducted (see ESI for detailed description). It reveals that Bi(III)@MIL-101 preserves immutable activity after at least four catalytic cycles (Fig. 5), significantly exceeding those for pure BiOCl. The

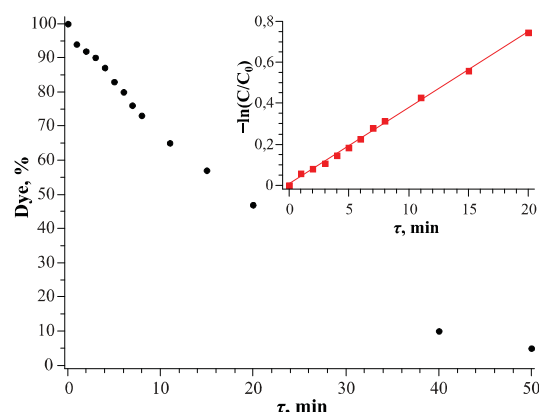

**Fig. 4.** Kinetics of methyl red degradation in presence of Bi(III)@MIL-101 under mercury lamp irradiation.

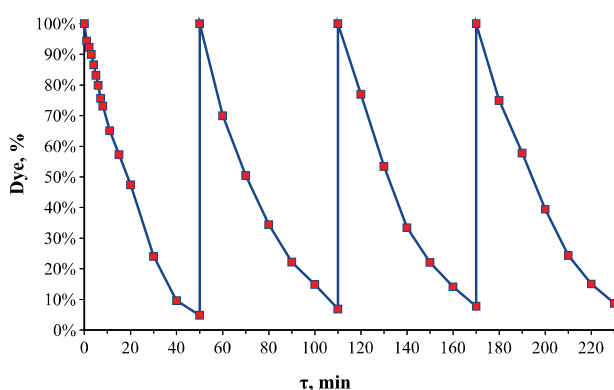

**Fig. 5.** Catalytic cycles of MR degradation in presence of Bi(III)@MIL-101 under mercury lamp irradiation.

full decolorizing of methyl red solution is observed in 20 min (see Fig. S9) when using 10 mg of BiOCl (8 mg of Bi) or in maximum 60 min when using 15 mg of Bi(III)@MIL-101 containing *ca.* 0.4 mg of Bi. So the specific activity of Bi(III)@MIL-101 catalyst is  $20/60 \cdot 8/0.4 = 6.7$  times higher than for pure BiOCl. While pure MIL-101 did not reveal any photocatalytic activity at all (Table S3), the enhancement behaviour of Bi(III)@MIL-101 is occurred due to stabilization of small oxo-hydroxo Bi(III) clusters immobilized in the cavities of MOF.

## EXPERIMENTAL SECTION

### General remarks

All chemicals and solvents were at least of analytical grade and were used as purchased without additional purification. PXRD data were obtained on a Shimadzu XRD 7000S diffractometer with  $\lambda$  Cu ( $K\alpha_1$ ,  $K\alpha_2$ ) = 1.54059, 1.54439. Element analysis on Cr, Bi and Cl was carried out by X-Ray fluorescence spectroscopy in several nanoscale points for control of samples uniformity using a Bruker MISTRAL M1 apparatus. An analysis of the porous structure was performed by a nitrogen cryoadsorption technique using automated gas sorption analyzer Autosorb iQ (Quantachrome Instruments) at 77 K. The samples were preliminary degassed in vacuum at 450 K for 12 hours.  $N_2$  adsorption-desorption isotherms were measured within the range on relative pressures of  $10^{-4}$  to 0.99. The specific surface area was calculated from the data obtained on the basis of the conventional BET and Langmuir models. The total pore volume was estimated from nitrogen uptake at  $P/P_0=0.95$ . The standard Saito&Foley approach, as the most appropriated for the studied materials, were employed to estimate the pore size distribution. Images of the samples were obtained by transmission electron microscopy using JEM 1400 instrument (Jeol, Japan) at 120 kV with standard sample preparation.

### Synthesis of compounds

**Synthesis of Cr-MIL-101.** The crystalline Cr-MIL-101 product was hydrothermally synthesized at 220 °C for 6 h from mixture of  $Cr(NO_3)_3 \cdot 9H_2O$  (1.2 g, 3 mmol), terephthalic acid (0.5 g, 3

mmol), 1 mL of 3 M HF (3 mmol) and 15 mL of water. Then the autoclave reactor was cooled to room temperature for 3 h to obtain larger crystals of the unreacted terephthalic acid which were removed by filtration using glass filter with a pore size between 40 and 100  $\mu m$ . Finally as synthesized solid was filtered off using paper filter. The purification procedure included two steps: double solvothermal treatment by DMF (50 mL of DMF per 1 g of MIL-101) at 60 °C for 2 h and then double treatment by EtOH at 75 °C for 2 h in the same MIL-101:solvent ratio. The resulting material was dried overnight at 80 °C under air atmosphere.

**Synthesis of Bi(III)@MIL-101.** In typical experiment 200 mg of MIL-101 was added to 2 mL solution of  $BiCl_3$  (20 mg) in 4 M HCl. After 30 min stirring at room temperature the green solid was filtered off and dried at 70 °C in air. After that the dry sample was put into 10% ammonia solution (21 mL). After 15 min stirring the solid of Bi(III)@MIL-101 was filtered off and dried at 70 °C in air again. Yield: 210 mg.

**Synthesis of BiOCl.**  $BiCl_3$  (100 mg) was dissolved in 10 mL of 1 M HCl solution. After that 20 mL of aqueous ammonia (1:2) was added to the solution under vigorous stirring. White solid obtained was filtered off, washed with water, ethyl alcohol and acetone. Yield: 37 mg.

### EXAFS-HERFD

High-energy-resolution X-ray absorption measurements were performed at the beamline ID26 of the European Synchrotron Radiation Facility. The electrons energy was 6.0 GeV, the ring electron current varied between 180 and 200 mA. The energy of X-ray incident beam was selected using the reflection from a double Si[111] crystal monochromator. Rejection of higher harmonics was achieved by two Si mirrors with a Pd and Cr layers located at 2.5 mrad angle relative to the incident beam. The energy calibration was performed using a Bi metal sample. High-energy-resolution fluorescence detection (HERFD) spectra were measured with an X-ray emission spectrometer at 12 K. The Bi HERFD spectra at the L3-edge were obtained by recording the intensity of the Bi  $L\alpha_1$  emission line (10839 eV) as a function of the incident energy. The emission energy was selected using the  $\langle 660 \rangle$  reflection of four spherically bent Ge crystal analyzers (with  $R = 1$  m). Each Bi HERFD-XANES scan was collected in 30 s with a step size of 0.1 eV and usually used averaging of 10–20 scans. Full Bi EXAFS-HERFD spectra over a 1000 eV range were measured in 180 s with a step size of 0.2 eV and averaging of 5 scans.

### Catalytic Tests

In typical experiment, 10–20 mg of catalyst (pure MIL-101, Bi(III)@MIL-101 or pure BiOCl) was heated at 100 °C until weight loss is stopped and then was put into 10 mL solution of methyl red ( $3.7 \cdot 10^{-5}$  M,  $10 \text{ mg} \cdot \text{L}^{-1}$ ). The mixture was irradiated by mercury lamp (1 kW) at room temperature (25–27 °C). Methyl red concentration was checked by UV-Vis ( $\lambda \approx 500 \text{ nm}$ ) with adding 0.1 M HCl solution for pH adjustment.



## Conclusions

To conclude, the hybrid photocatalyst — Bi(III) impregnated in the metal-organic framework matrix — has been obtained and tested, displaying an outstanding activity which exceeds that of pure layered BiOCl preparing in the similar synthetic conditions. The material Bi(III)@MIL-101 obtained is stable and active at least in four catalytic cycles, demonstrates truly heterogeneous nature of catalysis in azo dye photodegradation. According to EXAFS study the structure of oxo-hydroxo Bi(III) clusters inside MIL-101 cages was assumed. Interestingly, such a structure type is known but not very common for Bi compounds. These results allow us to propose that this strategy can be successfully expanded further 1) to other Bi(III) oxohalides and 2) to other MOFs with different porosity, controlling the size of Bi(III) polynuclear clusters and access of various organic substrates. This will yield a new family of highly active photocatalysts suitable for environmental applications.


## Acknowledgements

The work was supported by the Russian Science Foundation (Grant No. 14-23-00013).

## Notes and references

- S. Dong, J. Feng, M. Fan, Y. Pi, L. Hu, X. Han, M. Liu, J. Sun and J. Sun, *RSC Adv.*, 2015, **5**, 14610.
- C. C. Wang, J. R. Li, X. L. Lv, Y. Q. Zhang and G. S. Guo, *Energy Environ. Sci.*, 2014, **7**, 2831.
- G. Aragay, F. Pino and A. Merkoj, *Chem. Rev.*, 2012, **112**, 5317.
- R. K. Upadhyay, N. Soin and S. S. Roy, *RSC Adv.*, 2014, **4**, 3823.
- M. R. Hoffmann, S. T. Martin, W. Choi and D. W. Bahnemann, *Chem. Rev.*, 1995, **95**, 69.
- A. Di Paola, E. Garcia-Lpez, G. Marc and L. Palmisano, *J. Hazard. Mater.*, 2012, **211–212**, 3.
- J. Xiao, Y. Xie and H. Cao, *Chemosphere*, 2015, **121**, 1.
- S. Weng, Z. Pei, Z. Zheng, J. Hu and P. Liu, *ACS Appl. Mater. Interfaces*, 2013, **5**, 12380.
- A. Biswas, R. Das, C. Dey, R. Banerjee and P. Poddar, *Cryst. Growth Des.*, 2014, **14**, 236.
- W. Zhang, X. B. Wang, A. C. Wang, M. K. Wang, L. L. Long, W. Zhang, Q. Zhang and F. Dong, *Ind. Eng. Chem. Res.*, 2013, **52**, 6740.
- F. Tian, Y. Zhang, G. Li, Y. Liu and R. Chen, *New J. Chem.*, 2015, **39**, 1274.
- X. Liu, H. Yang, H. Dai, X. Mao and Z. Liang, *Green Chem.*, 2014, **17**, 199.
- F. Shen, L. Zhou, J. Shi, M. Xing and J. Zhang, *RSC Adv.*, 2015, **5**, 4918.
- W. Yang, Y. Wen, D. Zeng, Q. Wang, R. Chen, W. Wang and B. Shan, *J. Mater. Chem. A*, 2014, **2**, 20770.
- Y. Zuo, C. Wang, Y. Sun and J. Cheng, *Mater. Lett.*, 2015, **139**, 149.
- J. Hu, W. Fan, W. Ye, C. Huang and X. Qiu, *Appl. Catal. B Environ.*, 2014, **158–159**, 182.
- L. Lei, H. Jin, Q. Zhang, J. Xu, D. Gao and Z. Fu, *Dalt. Trans.*, 2015, **44**, 795.
- L. Ye, Y. Su, X. Jin, H. Xie and C. Zhang, *Environ. Sci. Nano*, 2014, **1**, 90.
- L. Ma, C. Abney and W. Lin, *Chem. Soc. Rev.*, 2009, **38**, 1248.
- M. O’Keeffe, *Chem. Soc. Rev.*, 2009, **38**, 1215.
- A. U. Czaja, N. Trukhan and U. Müller, *Chem. Soc. Rev.*, 2009, **38**, 1284.
- Z. Wang and S. M. Cohen, *Chem. Soc. Rev.*, 2009, **38**, 1315.
- L. E. Kreno, K. Leong, O. K. Farha, J. Roberts, K. A. Scheidt, S. T. Nguyen and J. T. Hupp, *Chem. Soc. Rev.*, 2009, **38**, 1450.
- N. Stock and S. Biswas, *Chem. Rev.*, 2012, **112**, 933–969.
- S. M. Cohen, *Chem. Rev.*, 2012, **112**, 970–1000.
- L. E. Kreno, K. Leong, O. K. Farha, M. Allendorf, R. P. Van Duyne and J. T. Hupp, *Chem. Rev.*, 2012, **112**, 1105–1125.
- M. Yoon, R. Srirambalaji and K. Kim, *Chem. Rev.*, 2012, **112**, 1196–1231.
- P. Horcajada, R. Gref, T. Baati, P. K. Allan, G. Maurin, P. Couvreur, G. Férey, R. E. Morris and C. Serre, *Chem. Rev.*, 2012, **112**, 1232–1268.
- N. V. Maksimchuk, K. A. Kovalenko, S. S. Arzumanov, Y. A. Chesalov, M. S. Melgunov, A. G. Stepanov, V. P. Fedin and O. A. Kholdeeva, *Inorg. Chem.*, 2010, **49**, 2920–2930.
- N. V. Maksimchuk, O. A. Kholdeeva, K. A. Kovalenko and V. P. Fedin, *Isr. J. Chem.*, 2011, **51**, 281–289.
- W. Salomon, F.-J. Yazigi, C. Roch-Marchal, P. Mialane, P. Horcajada, C. Serre, M. Haouas, F. Taulelle and A. Dolbecq, *Dalt. Trans.*, 2014, **43**, 12698.
- C. M. Granadeiro, A. D. S. Barbosa, S. Ribeiro, I. C. M. S. Santos, B. de Castro, L. Cunha-Silva and S. S. Balula, *Catal. Sci. Technol.*, 2014, **4**, 1416–1425.
- L. H. Wee, F. Bonino, C. Lamberti, S. Bordiga and J. A. Martens, *Green Chem.*, 2014, **16**, 1351–1357.
- C. M. Granadeiro, P. Silva, V. K. Saini, F. A. A. Paz, J. Pires, L. Cunha-Silva and S. S. Balula, *Catal. Today*, 2013, **218–219**, 35–42.
- J. Hermannsdörfer and R. Kempe, *Chem. - A Eur. J.*, 2011, **17**, 8071–8077.
- N. Cao, L. Yang, H. Dai, T. Liu, J. Su, X. Wu, W. Luo and G. Cheng, *Inorg. Chem.*, 2014, **53**, 10122–10128.
- Y. Huang, Z. Lin and R. Cao, *Chem. - A Eur. J.*, 2011, **17**, 12706–12712.
- Y. Pan, B. Yuan, Y. Li and D. He, *Chem. Commun.*, 2010, **46**, 2280.
- X. Li, Z. Guo, C. Xiao, T. W. Goh, D. Tesfagaber and W. Huang, *ACS Catal.*, 2014, **4**, 3490–3497.
- A. Dhakshinamoorthy, A. M. Asiri and H. García, *Angew. Chemie Int. Ed.*, 2016, **55**, 5414–5445.
- S.-R. Zhu, P.-F. Liu, M.-K. Wu, W.-N. Zhao, G.-C. Li, K. Tao, F.-Y. Yi and L. Han, *Dalt. Trans.*, 2016, **45**, 17521–17529.
- Z. Sha and J. Wu, *RSC Adv.*, 2015, **5**, 39592–39600.
- G. Férey, C. Mellot-Draznieks, C. Serre, F. Millange, J. Dutour, S. Surble and I. Margiolaki, *Science*, 2005, **309**, 2040–2042.
- E. A. Berdonosova, K. A. Kovalenko, E. V. Polyakova, S. N. Klyamkin and V. P. Fedin, *J. Phys. Chem. C*, 2015, **119**, 13098–13104.
- V. G. Ponomareva, K. A. Kovalenko, A. P. Chupakhin, D. N. Dybtsev, E. S. Shutova and V. P. Fedin, *J. Am. Chem. Soc.*, 2012, **134**, 15640–15643.
- A. C. Wibowo, M. D. Smith and H.-C. zur Loye, *CrystEngComm*, 2011, **13**, 426–429.
- D. L. Rogow, H. Fei, D. P. Brennan, M. Ikehata, P. Y. Zavalij, A. G. Oliver and S. R. J. Oliver, *Inorg. Chem.*, 2010, **49**, 5619–5624.
- Yi, Q.-F. Zhang, T. C. H. Lam, E. Y. Y. Chan, I. D. Williams and W.-H. Leung, *Inorg. Chem.*, 2006, **45**, 328–335.
- P. Thuéry, *Cryst. Growth Des.*, 2011, **11**, 3282–3294.

## Graphical Abstract and Synopsis

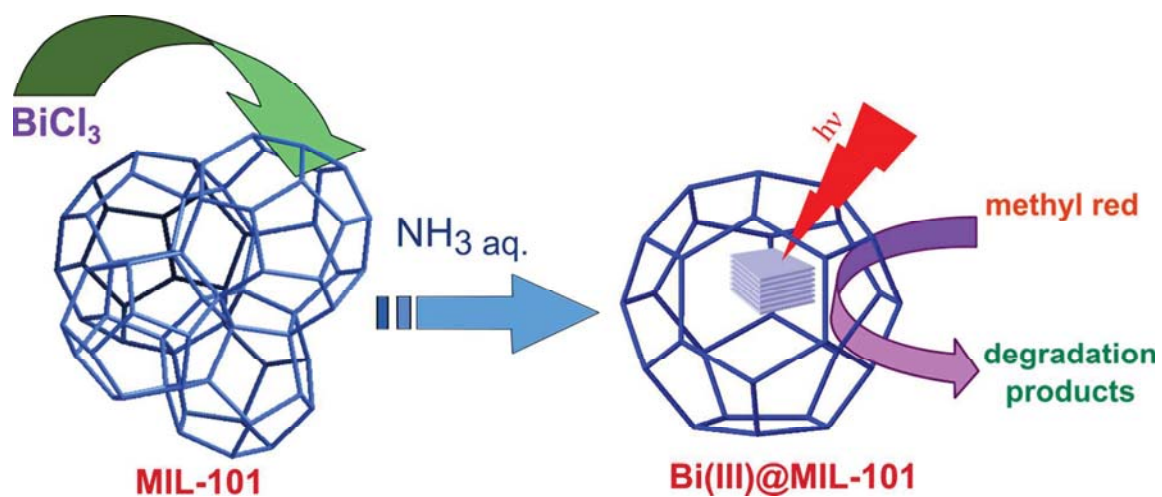

Bismuth(III) containing particles were immobilized into cages of mesoporous chromium oxoterephthalate MIL-101 using two-step approach. On the first step MIL-101 was impregnated by  $\text{BiCl}_3$  in hydrochloric acid solution and on the second step Bi-particles were fixed by hydrolysis in ammonia solution. Bi(III)@MIL-101 possesses enhanced photocatalytic activity in model reaction of methyl red degradation in comparison with bulk  $\text{BiOCl}$  obtained in the same synthetic conditions.